



Designation: F1306 – 21

Standard Test Method for Slow Rate Penetration Resistance of Flexible Barrier Films and Laminates¹

This standard is issued under the fixed designation F1306; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method permits flexible barrier films and laminates to be characterized for slow rate penetration resistance to a driven probe. The test is performed at room temperature, by applying a biaxial stress at a single test velocity on the material until perforation occurs. The force, energy, and probe penetration to failure are determined.

1.2 The values stated in SI units are to be regarded as standard. The values given in parentheses after SI units are provided for information only and are not considered standard.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.4 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 ASTM Standards:²

D618 Practice for Conditioning Plastics for Testing

E691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method

F2251 Test Method for Thickness Measurement of Flexible Packaging Material

2.2 ASQ Standards:³

ASQ/ANSI Z1.9 Sampling Procedures and Tables for Inspection by Variables for Percent Nonconforming

3. Terminology

3.1 Definitions of Terms Specific to This Standard:

3.1.1 *elongation (stretch)*—the elastic/plastic deformation of flexible sheet material under penetration by a driven probe.

3.1.2 *penetration resistance*—the ability of a flexible sheet material to withstand elongation and/or puncture by a driven probe.

3.1.3 *perforation*—the development of a measurable flaw through a barrier film undergoing penetration.

3.1.4 *probe penetration to failure*—distance probe travels from film contact to an instantaneous drop in load as observed on test equipment output.

3.1.5 *puncture*—the brittle elastic fracture of a flexible sheet material under penetration by a driven probe.

3.1.6 *universal testing apparatus*—machine capable of measuring tensile stress and compressive strength of materials.

4. Significance and Use

4.1 Penetration resistance is an important end-use performance of thin flexible materials where a sharp-edged product can destroy the integrity of a barrier wrap. This will permit package entry/exit of gases, odors, and unwanted contaminants, causing potential harm to the product and reducing shelf-life. Material response to penetration will vary with numerous factors, such as film thickness, elastic modulus, rate of penetration, temperature, shape and type of probe. Consequently, material responses from puncture to stretch may be observed and quantified using this method. Although numerous combinations of experimental factors can be devised and used to simulate specific end-use applications, the recommended conditions in this method should be followed for standard comparisons of materials.

¹ This test method is under the jurisdiction of ASTM Committee F02 on Primary Barrier Packaging and is the direct responsibility of Subcommittee F02.20 on Physical Properties.

Current edition approved Jan. 15, 2021. Published February 2021. Originally approved in 1990. Last previous edition approved in 2016 as F1306 – 16. DOI: 10.1520/F1306-21.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

³ Available from American Society for Quality (ASQ), 600 N. Plankinton Ave., Milwaukee, WI 53203, <http://www.asq.org>.

5. Apparatus

5.1 *Universal Testing Apparatus*, with a recording device.

5.2 *Compression Load Cell(s)*.

5.3 *Penetration Probe*, as in accordance with Fig. 1.

5.3.1 A 3.2 mm (0.125 in.) diameter hemispherical (biaxial stress) probe is recommended for general application and standard comparison of materials and interlaboratory results.

5.4 *Specimen Clamping Fixture*, as in accordance with Fig. 2 or equivalent. An apparatus that holds the sample securely, preventing material slip so that testing is not affected. Methods may include a pneumatic clamping mechanism or other mechanical means.

5.4.1 A sample test diameter of 35 mm (1.375 in.) is required for interlaboratory comparison of results. (If other probes are used, a minimum clamp to probe diameter ratio of 10 to 1 is required.)

5.5 *Specimen Cutter*.

6. Test Specimen

6.1 The test specimen shall be of uniform thickness ($\pm 2\%$ or 0.0025 mm (0.0001 in.), whichever is larger).

6.2 The dimensions of the test specimen shall be 76 mm by 76 mm (3 in. by 3 in.).

6.3 Where samples are multi-layer and not uniform in structure (ABC versus ABA), each side should be identified and treated as a different material, if penetration direction is important to material use, that is, inside versus outside of package.

7. Preparation of Apparatus

7.1 Consult the equipment operations manual for instructions to set up and operate the equipment.

7.2 Install probe apparatus.

7.3 Center probe over the fixture.

8. Number of Test Specimens

8.1 The number of samples tested should be adequate to be predictive of performance and relative to the purpose of the test. Caution should be taken when eliminating samples with defects as this can bias results. See ASQ/ANSI Z1.9 for guidance on sampling plans and practices to establish rationale.

9. Conditioning

9.1 Condition the test specimens at $23 \pm 2^\circ\text{C}$ ($73.4 \pm 3.6^\circ\text{F}$) and $50 \pm 5\%$ relative humidity for not less than 40 h prior to test in accordance with Procedure A of Practice D618 for those tests where conditioning is required.

9.2 Conduct tests in the standard laboratory atmosphere of $23 \pm 2^\circ\text{C}$ ($73.4 \pm 3.6^\circ\text{F}$) and $50 \pm 5\%$ relative humidity unless otherwise specified in this test method.

10. Procedure

10.1 Test equipment should be calibrated and within the calibration interval

10.2 Equipment load range should be such that specimen puncture occurs within 20 to 80 % of the same.

10.3 Using the specimen cutter, cut each sample material into a 76 mm (3 in.) by 76 mm (3 in.) piece.

10.4 Measure the caliper (average of 3 readings) in the center of a film specimen. Refer to Test Method F2251.

10.5 Adjust the universal tester cross head speed to 25 mm/min (1.0 in./min). Select a data acquisition rate to give a minimum resolution of 0.1 mm/point of penetration. (For chart recorders, set chart recording speed to 500 mm/min (20 in./min), if applicable.)

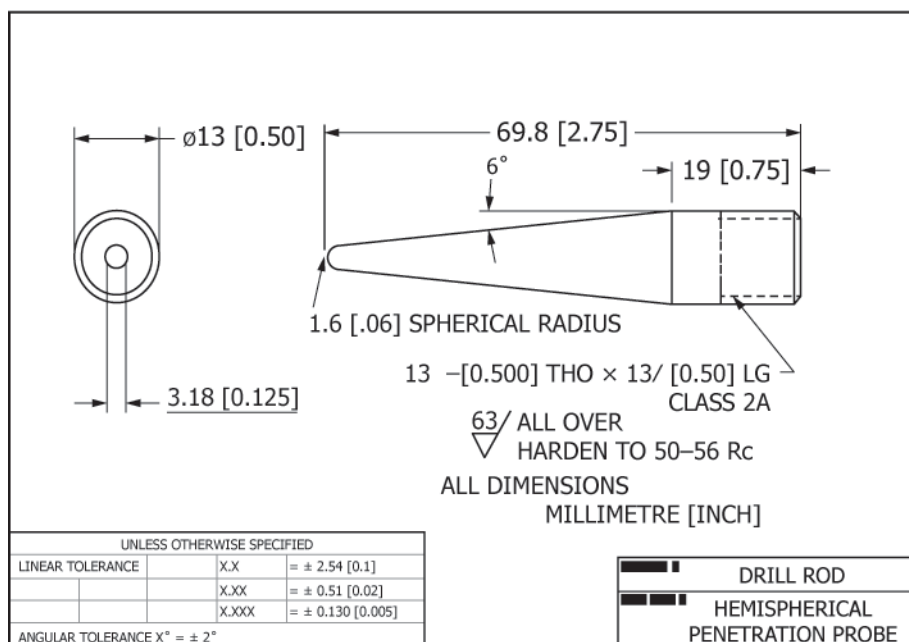


FIG. 1 Penetration Probe